

Spandrelite™ Glass

This document will provide the fabricator with the technical information necessary to successfully fabricate the Spandrelite™ glass product. The recommended procedures for proper processing of Spandrelite are described including storage, safety, and sound environmental management.

General:

Vitro *Spandrelite glass* is a pre-painted stock sheet that is easy to cut, fabricate and heat-treat. It utilizes a proprietary fritted coating. It must be heat treated (heat-strengthened or tempered) to achieve the designed appearance and performance characteristics. During the heat-treating process, the painted surface permanently bonds to the glass surface.


Spandrelite™ glass is intended for exterior applications. It may be used for commercial wall claddings or spandrel applications. The product is not appropriate for use in vision applications or any application where it is backlit and light is seen transmitted through the glass. These applications could cause imperfections, striations, or small pin holes to be observed, even when the painted surface meets all specifications for intended use. *Spandrelite™ glass* will typically be used in spandrel applications to cover or conceal construction materials between the floors of buildings.

When processing *Spandrelite™ glass*, the product should always be conveyed with the painted surface facing up and away from conveyor rolls and other conveyance surfaces, EXCEPT when cutting. The glass must be cut with the painted surface down against cutting table because a sufficient glass score is not obtainable through the painted surface.

When incorporated into an Insulating Glass Unit (IGU), *Spandrelite™ glass* must be positioned on the building interior surface of the unit only. Monolithic applications are permitted with the coating on the second (2nd) surface. First (1st) surface applications are not permitted. In the case of a double pane IGU, the *Spandrelite™ glass* painted surface must be located on the No. 4 surface. See 'Spandrelite Allowable Surface Positions' diagram below.

Spandrelite™ Glass

Spandrelite™ Allowable Surface Positions

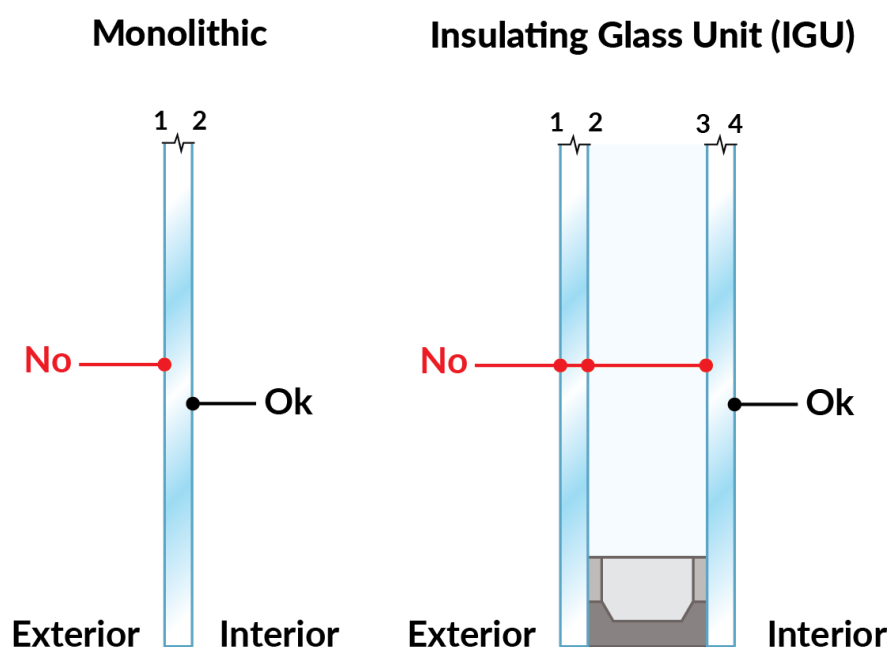

No coatings, frits, or any other substances are permissible to be placed on top of the *Spandrelite™ glass* painted surface before heat-treatment. Doing so will void the product Warranty.

When properly heat-treated, the *Spandrelite™ glass* painted surface provides a uniform attractive finish. Regardless of the particular configuration or application using *Spandrelite™ glass*, Vitro recommends that a full-size mock-up be viewed under the specific job-site conditions and retained as a basis for acceptable product.

Spandrelite™ Glass

Storage:

Storage of the product must be indoors away from exposure to the elements and in an area where fumes from sources such as de-mineralizers, acid storage, batteries, etc., cannot affect the product. As with all glass products, exposure to high humidity or direct water contact during storage should be avoided. There are no special handling requirements that have been identified for this product.

Spandrelite™ glass that arrives at your facility wet should not be accepted. Notify the glass carrier first and then Vitro.

As a general rule, care should be taken to avoid major fluctuations in temperature and humidity that may result in the formation of condensation on the glass or painted surface. These are generally encountered during glass transportation and storage. *Spandrelite™ glass* should not be impacted by minor inadvertent moisture contact. However, the presence of surface moisture may cause multiple glass sheets to adhere and make single lite free fall difficult. When surface moisture is present, Vitro recommends that the container be set aside until the glass surface is dry in order to limit the potential of multiple lites sticking together. If fans are available, they should be used to expedite the drying process.

Glass should be processed through heat treating within six months of receipt. FIFO should be practiced. Ideal storage conditions are temperatures less than 86°F, and 70 - 75% relative humidity. Inventory should be routinely inspected if not used in a timely manner for any visible degradation of the painted surface. If the storage area is not environmentally controlled, air movement is an important factor to help prevent degradation. Large fans can be installed to assist with air circulation. One vendor of storage solutions, fans, and monitoring systems is BigAss Fans: <http://www.bigassfans.com>.

Handling:

No special handling guidelines have been identified but Vitro suggests avoiding all unnecessary contact with the painted surface. The *Spandrelite™ glass* surface should never be handled with bare hands. Clean, non-marking, dry gloves must be worn when handling the product.

If a lift assist using suction cups is attached to the painted surface during handling, the suction cups must be clean and dry. Care should be taken to ensure the suction cups do not slip on the painted surface. Evaluations should be made of the painted surface after cup contact to ensure the cups do not damage the painted surface or leave a residue.

If self-adhesive stickers/labels are used to identify the glass during production, the adhesive side of the sticker should not be in contact with the painted surface.

Spandrelite™ Glass

Cutting:

Spandrelite™ glass can be cut using conventional scoring and breakout equipment. **The painted surface must be face down against the table surface during cutting so that the unpainted surface of the glass gets scored. The glass cannot be scored sufficiently through the painted side.** The cutting table surface must be clean (free of glass chips and debris) and not saturated with cutting oil prior to processing.

When cutting *Spandrelite™ glass*, it is recommended that cutting fluid be used in moderation to lubricate the cutting wheel and achieve the optimal scoring of the glass. Any of the cutting fluids on the Vitro approved list can be used with *Spandrelite Glass*. Excessive cutting fluid should be avoided so that it will not run down the glass when it is placed in a vertical position. See TD-149, *Acceptable Cutting Fluids and Detergents for use with Vitro's MSVD Sungate® and Solarban® Coated Glass Products* for a list of acceptable cutting fluids.

Vitro recommends using the standard cutting parameters for uncoated 6mm glass including the standard wheel angle, pressure, and cutting speed. No special set-ups are required. See TD-119, *Guidelines for Glass Scoring and Breakout Quality* for additional information and recommendations regarding conventional glass cutting.

Vitro recommends a minimum 1" trim be taken in order to properly breakout *Spandrelite™ glass*. Vitro recommends that you take trim on all four (4) sides when cutting. This will reduce the chance of any paint overspray that may be present on the glass edges of received product from potentially being transferred to the furnace rollers.

It is recommended that *Spandrelite™ glass* cut-size that is staged between processing steps be separated with foam-covered cork tabs or polyfoam strips in the corners if lites of different dimensions are stacked adjacent to one another. Attach cling side of cork tab to the painted surface. Cutting fluid should not be allowed to dry on cut-size glass before the next processing step.

Spandrelite™ Glass

Spandrelite™ glass trim cannot be returned to glass manufacturing plants. It is recommended that all glass trim from cutting operations be recycled if possible first, and then discarded in an approved landfill as regular nonhazardous waste second. See 'Disposal' section.

Note: These guidelines are suggested starting points and further adjustments may be needed to optimize the cutting and break-out results for your specific cutting machine and process setup. As always, the cut edge quality should be visually inspected for excessive chips, sharks teeth, and other defects that will affect the glass strength and appearance.

Seaming:

Spandrelite™ Glass can have the glass edges seamed using conventional seaming equipment. Seaming will be similar to that of other glass products. The painted surface must always face up away from the conveyor or table during seaming to avoid the possibility of debris scratching the painted surface. The seaming table must be cleaned frequently. Contact with the painted surface must be minimized during seaming. Contact should be made from the edges or with the unpainted surface. Only clean, non-marking, dry gloves should be worn when handling the product.

Dry seaming is the preferred and recommended method, but wet seaming is also acceptable. If wet seaming is used, the glass should be washed and dried immediately thereafter to ensure that none of the seaming liquid is allowed to dry on the glass. The optimal seaming belt abrasive is 120 grit. Inspect belt quality more frequently when dry seaming *Spandrelite™ glass* and change belts when necessary.

Washing:

Spandrelite™ Glass can be washed using standard float glass washer settings. The painted surface must always face up away from the conveyor when using horizontal washing equipment or facing the operator (away from rollers) in vertical washing equipment to avoid the possibility of debris scratching the painted surface. Low-e type brushes, although not required, are still preferred. Good washer practices should be followed including having a pre-spray section that floods the painted surface with clean water, maintaining wash water temperature between 110 and 140°F, and maintaining total dissolved Solids (TDS) of the final rinse tank below 20 ppm. See TD-144, *Recommended Techniques for Washing Glass* for additional information and recommendations regarding conventional glass washing.

Spandrelite™ Glass

Wash water detergents on the approved list for Solarban products may be used. See TD-149, *Acceptable Cutting Fluids and Detergents for use with Vitro's MSVD Sungate® and Solarban® Coated Glass Products* for a list of acceptable detergents.

Note: At no time should any portion of the glass be allowed to stop inside the washer.

Even if water, brush rotation, and air-knife blower(s) are programmed to stop when glass stops, there is a risk that some of the *Spandrelite™ glass* painted surface will have a different appearance if glass is stopped in the washer. This difference may not be visible until after heating.

It is also important to ensure that *Spandrelite™ glass* exits the washer completely dry to help ensure uniform appearance post-heating, prevent streaking, and prevent adherence issues.

Heat Treating:

Spandrelite™ glass must be heat strengthened or fully tempered to fuse the paint to the glass substrate. It can be heat treated in a manner very similar to uncoated glass of the same thickness and substrate, but may require more heating time in the furnace in order to get the paint to fire properly. *Spandrelite™ glass* should be processed on one furnace for all tempering runs for each project, if possible, to help ensure consistency of final product. All attempts should be made to minimize the number of tempering batch runs for each project. **The glass must be run painted surface up through the furnace to prevent paint transference to the ceramic rollers.**

The white product will likely require more cycle time than the black or gray in order to ensure full fusing of the paint to the glass surface. The additional amount of time should be confirmed based on testing described in the 'Adequate Paint Firing' section below.

Spandrelite™ Glass

To heat the *Spandrelite™ glass* product, start with your 6mm Clear uncoated glass recipe. For the black product, increase the total heating time by approximately 10%, keeping the heat set points unchanged. For the gray product, increase the cycle time by about 15%, and for the white product, increase heating time by about 20%, again leaving all other parameters unchanged. See Summary Table below.

Spandrelite Heating Time Guidelines

Product	6mm Clear	Black	Warm Gray	White
Heating Time (Cycle Time)	Standard Recipe	6mm Clear Standard + 10%	6mm Clear Standard + 15%	6mm Clear Standard + 20%

If you can adjust the convection heating across the width of the furnace, apply more heat to the middle third to half of the plate width to ensure the paint adheres properly to the glass in the center. If the glass becomes too hot (causing distortion, edge kink, roller-wave, etc.), reduce the total heating time by 2 seconds per millimeter of glass thickness and repeat until all quality metrics are met.

If you notice any blistering of the paint, ensure the product is completely dry after washing and that the furnace convection heat is not too high. You may need to lower the heating set points and extend the heating time to ensure sufficient heat penetrates through the glass body without overheating the painted surface.

Do not run *Spandrelite™ glass* through the heating process more than once as mechanical properties, color, and gloss can be adversely affected.

Refinements will be made by the furnace operator as they gain experience with this product as it processes through the fabricator's specific equipment. The final tempering/heat strengthening recipes will reflect the settings required to produce a quality product that satisfies the requirements of either heat strengthened or fully tempered glass as defined in ASTM C1048, as well as the particle size requirements of fully tempered glass approved for safety glazing as defined in ANSI Z97.1, all the while maintaining acceptable distortion characteristics.

Spandrelite™ Glass

Insulating:

Spandrelite™ glass is approved for Spandrel and IGU applications. See TD-145, *Spandrel Glass Types and Recommendations* for additional information and recommendations. NOTE, however, that *Spandrelite™ glass* can only be installed on the inside building surface of an IGU (#4 surface if dual pane IGU) or the #2 surface of a monolithic application. The painted surface of *Spandrelite™ glass* must not be installed inside the sealed airspace of an IGU.

Edge deletion is not required since the painted surface will not be installed on an interior surface of an IGU where the painted surface would be in contact with a spacer material or IGU sealant.

For glazing sealants, the glazing sealant manufacturer is responsible for testing/verifying that their products are compatible with the *Spandrelite™ glass* painted surface. Vitro will provide samples if requested. When properly fired, the *Spandrelite™ glass* painted surface has properties similar to the glass.

Other Fabrication Considerations:

Bending

The *Spandrelite™ glass* product should not be used in bent applications. Doing so will void the product warranty.

Lamination

Lamination of this product with the *Spandrelite™ glass* painted surface touching the interlayer is not approved and voids the *Spandrelite™ glass* warranty. This could change the appearance of the painted surface leading to visual mismatch complaints. Lamination with interlayer touching the unpainted side of the *Spandrelite™ glass* is acceptable.

Thermal Stress

Breakage due to thermal stress is not typically a concern since the product MUST be heat-treated. However, there is one potential exception to this. From Vitro TD-145, *Spandrel Glass – Types and Recommendations*:

Vitro recommends that glass used in spandrel applications be heat strengthened except for the interior lite of an insulating glass unit spandrel when the application uses a low-e coating and a medium to dark opacifier combined with insulation on or very near the back of the spandrel unit. In these instances, tempered glass for the interior lite of spandrel unit may reduce the probability of breakage due to thermal stresses.

Spandrelite™ Glass

In the case where gray or black *Spandrelite™ glass* is on the building facing interior surface of an IGU, and a low-e coating is used facing an airspace in the IGU, tempering of the *Spandrelite™ glass* may be necessary and a thermal stress evaluation should be considered.

Quality Guidelines:

Adequate Paint Firing

Testing must be done on a regular basis to ensure heat-treated *Spandrelite™ glass* product conforms to all quality requirements. Any product that does not meet requirements should be quarantined and/or destroyed and corrective action must be taken. Vitro recommends that all quality checks be recorded, and records maintained for ten years.

Note: When fully tempering the Spandrelite™ glass product, even if you pass the particle weight test according to ANSI Z97.1 or CPSC 16 CFR 1201, you cannot be sure you have achieved full fire of the paint with the glass substrate based on that test alone. The same can be said for passing the GASP stress test in the case of the heat-strengthened product. Further testing is required to ensure full paint fire.

Vitro requires at least one test based on ASTM Standard C1048, Section 10.2 'Test for Porosity' to ensure the paint has fully fused to the glass substrate in representative areas across the entire plate. Vitro recommends performing a Permanent Marker Pen Test first, followed by some form of Scratch (mechanical durability) testing.

Spandrelite™ Glass

Marker Test

For the marker test, apply a black permanent ink mark to the painted surface of the lite in five evenly spaced locations, one toward each corner and one in center (for white and gray products). For the black *Spandrelite™ glass* product, you can use a silver-colored permanent marker. When viewed from the unpainted side, the mark should not be visible. If there is any doubt, try to clean the mark off the painted surface with glass cleaner and clean cloth, then re-view from the unpainted side. The marks should be noticeably reduced in appearance. Use standard ambient lighting when performing this test, no spotlighting or backlighting. An opaque background is best. You are looking to ensure the ink doesn't bleed through the paint to the glass surface. See photos below from successful marker test.



Paint Side



Glass Side

Water Drop Test

For the wet test, apply a drop of water to the painted surface and lightly rub it into the surface with a finger or swab. When viewed from the non-painted side, the moistened areas should not be visible.

Spandrelite™ Glass

Scratch Test

Vitro also recommends performing a Scratch Test on the *Spandrelite™ glass* product. The painted surface is intentionally scratched with a pointed object. A sclerometer set to 20N force is very useful for this test and should be drug across the painted surface in multiple locations. Scratches made in the paint should not be visible from the non-painted side using ambient lighting. One outlet for obtaining a sclerometer is through Elcometer:

[Sclerometer Hardness Tester | 3 ranges | Elcometer 3092 \(elcometerusa.com\)](#)

Gloss Measurements

It is also recommended that gloss readings be recorded and maintained for all products ***that have already passed the permanent marker and/or scratch testing.*** Variation in gloss can correlate to unacceptable variation in unit-to-unit appearance. Gloss meter readings (60-deg Specular) can vary considerably from meter to meter, so it is recommended you standardize on one meter only for all project gloss readings. You should take approximately three gloss readings each from ten *Spandrelite™ glass* pieces that have passed porosity testing, and that appear uniform visually under various lighting and viewing conditions. Average the readings. For the remainder of the batch run and/or project, it is recommended that you target gloss readings to fall within average value +/- 15 Gloss Units, making sure you use the same meter for all subsequent measurements. Sample approximately 10% of production for acceptable gloss range.

Visual Inspection

After heat treatment, *Spandrelite™ glass* should be evaluated visually for pinholes, striation lines, scratches, abrasions, voids, and contaminants per ASTM C1376 Specification guidelines, using the quality specifications designated for glass classified as 'Kind CS' for coated spandrel/non-vision glass.

Initially, the glass should be inspected using transmitted lighting, viewing the glass from the non-painted side. A diffused light source of 1700-2500 lux should be used behind the glass, not spotlight or sunlight, placed no closer than 12" to the glass. Stand or hold sample at approximately arm's length distance, and no blemishes should be readily apparent. If blemishes are apparent, reinspect from 15 feet away, using the table below to determine if blemishes are acceptable. No more than two readily apparent blemishes are allowed in a 3" diameter circle, and no more than five readily apparent blemishes are allowed in a 12" diameter circle.

Reinspect Readily Apparent Blemishes from 15 Feet Using the Following Criteria

Pinholes	<= 1/16"
Spot	<= 1/16"
Coating Scratch (length)	<= 3"
Mark/Contaminant (length)	<= 3"
Coating rub (length plus width)	None allowed
Crazing (length plus width)	<= 2"
Corrosion	None allowed

Spandrelite™ Glass

Some striation lines are expected to be seen occasionally in the white or gray product after heating, when viewed in transmission. As long as you cannot see them when viewed in reflection (no backlighting) from 15 feet away, they should not create a visual difference once installed. If it is desired to try to reduce striation lines, you can increase heating time in the furnace.

Touch-Up Paint

Touch-Up Paint is available on Shopify from Vitro in all three *Spandrelite™ glass* colors. This can be used to correct minor blemishes and scratches that can be seen when performing the visual inspection checks described above. The paint can be applied with a small paint brush that comes with the cap, and should only be applied after heating the product. Allow to air dry. For information on obtaining Touch-Up Paint, consult

https://8tvv7ftpee8okuzs49250730140.shopifypreview.com/products_preview?variant=50506619125991

or visit Vitro's sample website.

Overall Bow/Warp

Just like with 6mm commercial product, ASTM C1048 requirements for overall bow/warp should be met.

Color Monitoring

Job color uniformity within each color of *Spandrelite™ glass* processed, both within and between tempering runs, is critical. If evaluating color with a spectrophotometer, it is recommended that, at a minimum, *Spandrelite™ glass* product be evaluated for color at run start-up, and periodically throughout each production run with an initial recommendation of 5% sampling of all products produced within one batch run, evenly distributed. The spectrophotometer should be calibrated before each run. The glass color should be evaluated by taking readings from the non-painted surface. A minimum of three readings, preferably across the diagonal of the lite, are recommended. Readings (L^* , a^* , b^*) within one lite should be compared to reference target values that you have gained from your process averages, using a standard DE^*ab calculation (see Vitro TD-516 *Solarban® Color Uniformity* for reference), and DE^*ab should not exceed 4.0. If you desire specific color reference value guidelines (Reflected Glass Side L^* , a^* , b^*) for the *Spandrelite™ glass*, please consult with Vitro Technical Services.

Recycling

Spandrelite™ glass can be recycled. Consult with vendors in your area.

Disposal

The disposal of *Spandrelite™ glass* does not present any additional health or safety hazard. *Spandrelite™ glass* is not "hazardous" as defined by the federal Resource Conservation and Recovery Act (RCRA). Arrange

Spandrelite™ Glass

for proper disposal in landfill, complying with applicable Federal, State, and local regulations, if a recycling vendor cannot be contracted to remove product waste.

Additional Information

Every effort has been made to ensure the accuracy of the information in this document. This information is intended to assist in the proper application and use of *Spandrelite™ glass* and does not constitute a warranty of this product for any particular purpose.

If you require additional information or technical support with this product or any other flat glass products, please contact your Sales Representative or the Technical Service Group at 412-820-8500.

HISTORY TABLE		
ITEM	DATE	DESCRIPTION
Original Publication	4/1/25	Initial Release

This document is intended to inform and assist the reader in the application, use, and maintenance of Vitro Flat Glass products. Actual performance and results can vary depending on the circumstances. Vitro makes no warranty or guarantee as to the results to be obtained from the use of all or any portion of the information provided herein, and hereby disclaims any liability for personal injury, property damage, product insufficiency, or any other damages of any kind or nature arising from the reader's use of the information contained herein.

Acuity®, Atlantica®, Azuria®, Clarvista®, EcoArmor™, Graylite®, Herculite®, Intercept®, Optiblue®, Optigray®, Pacifica®, Pavia® Acid-Etched glass, Platia® Mirror glass, Solarban®, the Solarban® logo, Solarblue®, Solarbronze®, Solarcool®, Solarvolt™, Solexia®, Spandrelite™, Starphire®, Starphire Ultra-Clear®, the Starphire® logo, Sungate®, Sungate ThermL™, Vistacool® glasses, Vitro® and the Vitro logo, VacuMax™, Vitro Authorized™, Vitro Certified™ and the Vitro Certified™ logo are trademarks owned by Vitro and its subsidiaries.